
KINETICS AND THERMODYNAMIC BEHAVIOR OF SOME PREPARED BENZIMIDAZOLE AND CHROMENE DYES ON POLYESTER FIBRE.

M. S. ABOUL-FETOUH, S.SHAKRA**, A.-B. GHATTAS*** and F. EL SAYED HASSAN*.*

Chemistry Department, Faculty of Science, Al-Azhar University, Nasr City, Cairo , Egypt.

** Textile Research Division, National Research Centre, Dokki, Cairo, Egypt.

***Chemistry Department, Faculty of Science, Sohag University, Egypt.

Abstract

Diffusion as a function of temperature of benzimidazole and chromene dyes. It is well known that a carrier is not required for the dyeing of polyester at temperature exceeding 100° C (high temperature dyeing process). This is due to the fact that the diffusion coefficient increases with rising temperature. The extent of this increase was found by measuring exhaustion curves at different temperatures.

Introduction

The dyeing process in case of polyester and wool was carried out near the boiling. It was expected that the dependence on temperature of these diffusion D_T value would be in accordance with the relation:

$$D_T = D_o e^{-E/RT}$$


Where $D_o = K$ is a constant. E is the molar energy of activation. T is the absolute temperature and R is the general gas constant. A straight line must be obtained when $\ln k$ is plotted against $1/T$. The energy of activation E can then be calculated from the slope of this straight line.

By the same method we can determine the free energy at different temperature by the law⁽¹⁻⁶⁾.

$$\begin{aligned} -\Delta G_T &= RT \ln [D_f] / [D_s] \\ \Delta H^0 &= \Delta G_{100}^0 + T_{100} \Delta S^0 \end{aligned}$$


Experimental:

The chemical structures of the synthesized dyes are:

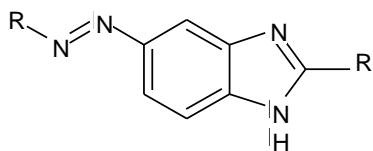

I - III

I, R¹ = H; II, R¹ = CH₃; III, R¹ = CF₃.

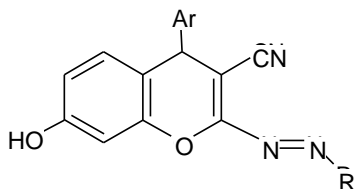


IV & V

IV, -Ar = phenyl; V, Ar = 4-chlorophenyl.

I, II & III:

R=

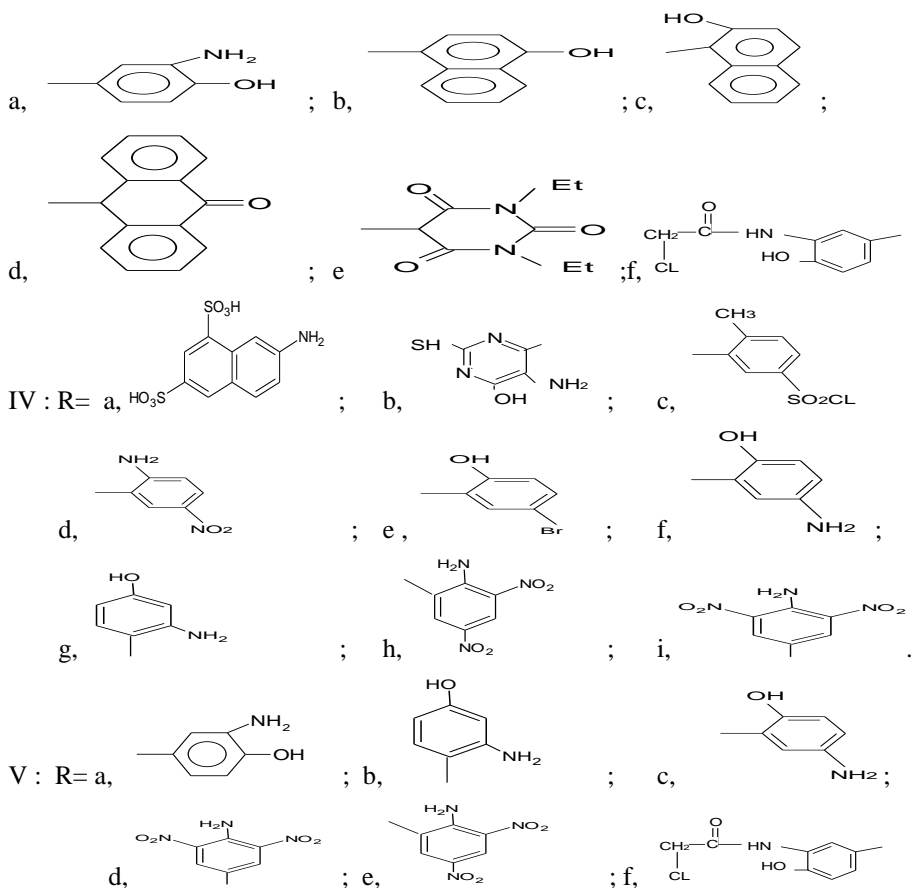

The syntheses of these dyes were described in another submitted article⁽⁷⁾.

Dyeing Exhaustion curves:

The rate of exhaustion was determined by measuring the optical density of the dye bath solution at different periods up to two hours, using lambda - 3B-spectrophotometer .

II- Materials for dyeing.

Polyester, Polyester woolen type denir 1.4 and wool produced locally at (Misr Rayon Co. Kafr El Dawer and El Mehalla El Kubra), Egypt.

III. Instrumentation and measurements.

- 1- Melting Point apparatus 2- Spectrophotometric analysis
- 3- Colour measurements.

Results and Discussions

The rate of exhaustion of the dyeing bath was measured near the boiling by measuring the optical density of the dye bath solution at the previously predetermined λ max for each dye initially and after different periods of time 5,15,25and 120 minutes⁽⁸⁾.

$$\% \text{ Exhaustin} = \frac{A_{so} - A_{st}}{A_{so}} \times 100$$


Where A_{so} = Absorbance at zero time
 A_{st} = Absorbance at time (t)

Table (1): % of Exhaustion of disperse dyes on polyester fibre at corresponding different time .


Time Dye No	% fexhaustion on polyester fibre										
	20	40	60	80	100	Dye No	20	40	60	80	100
I a	44	56	68	72	82	f	43	59	71	75	78
b	40	54	68	72	80	IV a	54	68	76	82	88
c	36	50	62	70	74	b	50	62	72	79	82
d	38	48	59	70	76	c	48	60	70	74	80
e	42	50	63	72	81	d	50	58	68	70	78
f	40	56	69	73	80	e	50	58	64	74	82
II a	48	60	68	76	84	f	52	58	66	76	84
b	42	56	62	72	80	g	50	56	64	72	80
c	39	54	62	70	78	h	54	68	76	82	88
d	39	54	62	70	78	i	52	58	66	78	86
e	40	54	62	70	79	Va	50	62	72	79	82
f	35	54	67	71	75	b	48	60	70	74	80
III a	52	58	68	78	86	c	38	54	67	71	75
b	50	59	67	79	84	d	52	58	68	78	86
c	48	58	66	80	82	e	50	58	68	76	84
d	42	58	64	74	80	f	40	54	62	70	78
e	40	54	62	70	78						
% of exhaustion of group III dyes on wool fibre											
III a	55		65		76		82		90		
b	52		62		72		80		90		
c	50		60		71		80		90		
d	52		62		72		80		90		
e	54		64		74		82		92		
f	54		70		82		86		88		

The results obtained indicate that the dye uptake increased with the increase in time of dyeing. The increased dye up take with the increase of time of dyeing can be

attributed to the need of the dye molecule to diffuse inside the fibre and reached to maximum dye up- take.

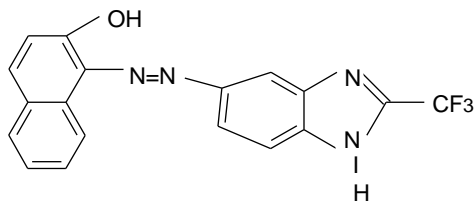

IIIc

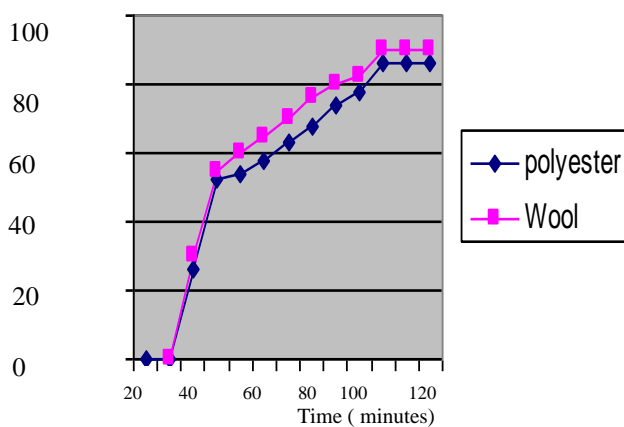



Exhaustion Curves on polyester and wool of III c dye

Fig.,(1)

Table (2): Equilibrium dye up take % and rates of dyeing of PET fibre with disperse dye groups I- V.

Dye No	Polyester			Fibre			
	Equilibrium dye up take	$T_{1/2}$ min	Velocity Con. $K \times 10^{-3} \text{ min}^{-1}$	Dye No	M_{∞}	$T_{1/2}$ min	$K \times 10^{-3} \text{ min}^{-1}$
I a	82	22.73	14.12	f	78	23.25	15.75
b	80	25.0	12.5	IV a	88	18.5	18.04
c	74	27.78	12.8	b	82	20.0	19.05
d	76	26.32	13.16	c	80	20.8	18.75
e	81	23.8	13.29	d	78	20.0	13.49
f	80	25	12.5	e	82	20.0	19.05
II a	84	20.8	15.8	f	84	19.2	19.35
b	80	23.8	13.8	g	80	20.8	19.0
c	78	25.6	12.8	h	88	18.5	18.0
d	78	25.6	12.8	i	86	18.5	18.1
e	79	25.0	12.98	Va	82	22.7	14.1
f	75	28.57	11.67	b	80	25.0	12.5
III a	86	19.2	17.78	c	75	28.5	12.0
b	84	20.0	17.5	d	86	19.2	17.8
c	82	20.8	17.2	e	84	20.0	17.2
d	80	23.8	13.8	f	78	23.25	16.0
e	78	25.0	13.49				

The results obtained indicate that the dye uptake increased with the increase in temperature of dyeing. The increased dye up take with the increase of temperature of dyeing can be attributed to the need of the dye molecule for high thermal energy to over come the energy barrier of the fibre water interface⁽⁹⁾

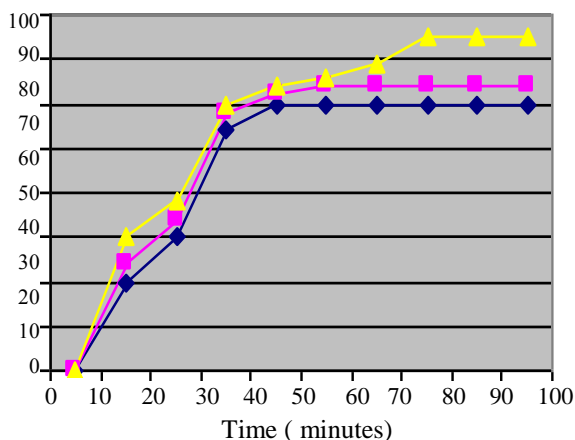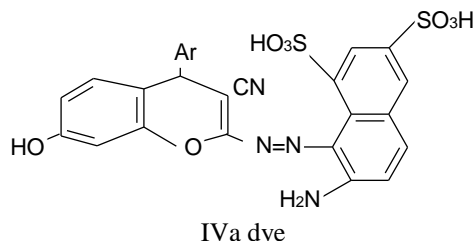



Exhaustion curves on polyester fibre of dye No IVa at different Temp

Fig.,(2)

Table (5): % of exhaustion of dyeing of PET/wool, and wool fibre .

Dye No	% of exhaustion on wool fibre						% of exhaustion on polyester/ wool				
	Time	0	20	40	60	80	100	20	40	60	80
I _f	0	51	67	80	84	90	40	56	69	73	80
II _f		48	65	78	82	85	35	54	67	71	75
III _f		54	70	82	86	88	43	59	71	75	78
IV _d		56	71	84	88	88.5	45	60	73	77	80
IV _e		58	72	86	90	90	47	61	75	79	81

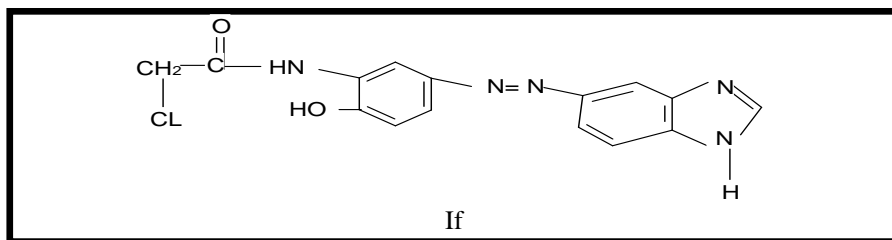

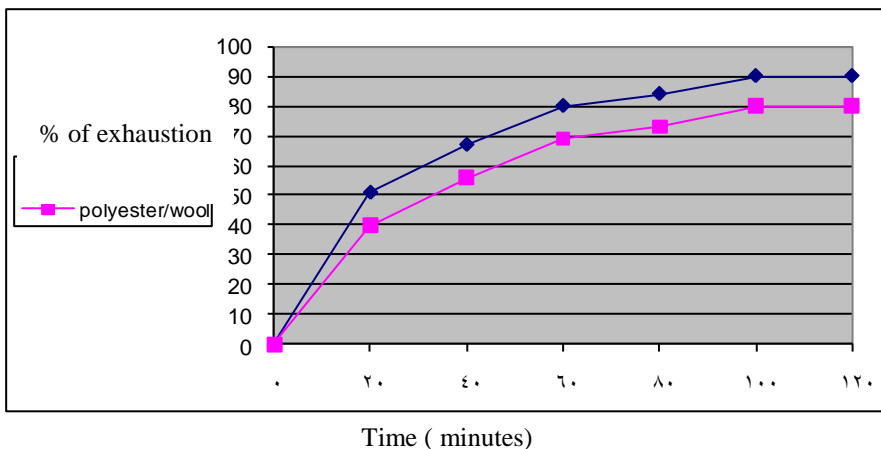

Exhaustion curves on wool, polyester / Wool, of dye No If
Fig.,(3)

Table (6): Equilibrium dye up take % and rate of dyeing of PET/ wool, and wool fibre with substantial disperse dye I_f, II_f, III_f,IV_d, IV_e at 100c

Dye No	Polyester/wool			Wool		
	Equilibrium dye lake %	T _{1/2} min	Velocity k.10 ⁻³ min ⁻¹	M _d %	T _{1/2} min	Velocity k.10 ⁻³ min ⁻¹
I _f	80	25	12.5	90	19.6	14.53
II _f	75	28.57	11.67	85	20.8	15.26
III _f	78	23.25	15.75	88	18.5	18.04
IV _d	80	22.2	16.08	88.5	17.85	19.47
IV _e	81	21.28	17.06	90	17.24	20.14

Table (7): Exhaustion % of substantial dyes I_f, II_f, III_f,IV_d, IV_e by polyester/wool, and wool at different temperature.

Temp Dye No	Exhaustion%											
	Polyester / wool						Wool					
	50:c	60:c	70:c	80:c	90:c	100:c	50:c	60:c	70:c	80:c	90:c	100:c
I _f	54	58	64	68	75	80	58	67	75	78	82	90
II _f	51	52	58	62	68	75	54	64	69	72	75	85
III _f	51	53	55	58	66	78	54	62	69	71	79	88
IV _d	51	54	58	60	72	80	52	57	59	65	73	88.5
IV _e	51	55	65	68	74	81	53	60	70	76	84	90

Thermodynamic behavior of some prepared dyes on polyester fibre ⁽¹⁰⁾.

Table (8): Calculation of ΔG, ΔG/T, 1/T for the prepared dyes under investigation.

Dye No	(T) ^o K	-ΔG ^o ×10 ³	$\frac{\Delta G}{T}$	$\frac{1}{T}$
I a	323	0.21	0.65	3.1×10 ⁻³
	333	0.47	1.41	3×10 ⁻³
	343	0.83	2.42	2.9×10 ⁻³
	373	1.13	3.03	2.7×10 ⁻³

Table (9) :- Thermodynamic function of some dyes

Dye No	ΔE	$-\Delta G \times 10^3$	$\Delta H \times 10^3$ K.cal.	$-\Delta S$ cal \circ K $^{-1}$ mole $^{-1}$
I _a	780	1.13	7.6	87.3
II _a	1050	1.24	8.0	92.4
III _a	1150	1.36	7.35	87.1
IV _a	850	1.94	5.0	64.9
I _f	815	1.04	5.2	62.4

The results obtained from table (9) indicate that:

1)- ΔG ranged from 1.04-1.94 positive value indicate the real dyeing process on polyester fibre sample.

2)- ($-\Delta S$) ranged from 62.4-92.4 cal K $^{-1}$ mole $^{-1}$ high positive value this \circ indicate that the dye molecule inside the fibre is regular and arrangement inside the fibre this module for completing dyeing process

3)- $|\Delta H|$ ranged from 5-8 K cal this indicate that the dyeing process completing by diffusion controlled not by chemical bonding reaction which has the $|\Delta H|$ value ranged from 18-27 K .cal.

4)- ($-\Delta H$) has positive value ranged from 5-8 k.cal this indicate that the dyeing process is exothermic process.

Conclusion

From this research of benzimidazole and chromene dyes found that:

- ΔG ranged from 1.04-1.94 positive value indicate the real dyeing process on polyester fibre sample.

- ΔS ranged from 62.4-92.4 cal K $^{-1}$ mole $^{-1}$ high positive value this \circ indicate that the dye molecule inside the fibre is regular and arrangement inside the fibre, also bonded suggesting module for completion of dyeing process

$-\Delta H$ has positive value ranged from 5-8 k.cal this indicate that the dyeing process is exothermic process.

References :

1. H.A.M., El-ADAWY, Ph.D. Thesis, " A study of Some Recent Techniques For Removal of color in textile Mills" Faculty , Al-Azhar University, Cairo, Egypt.(2011).
2. A.Urbanik, *Textilverdlung*, 13,279,(1980).
3. A.T.Peters, J., *Chem., Tech., Biotechnol.*, 53,301,(1992).
4. B.C.Burdentt, *Rev., Prog., Coluration*, 13,41,(1983).
5. J.Odvarka, *JSDC*, 99,207,(1983).
6. A.T.Peters, *JSDC*, 104, 344, (1988).
7. S.Shakra, M.S.Aboul-Fetouh, A.-B.Ghattas and F. EL Sayed Hassan (Submitted).
8. H.S.M., Nassar , Ph . D. Thesis," Some Physico . Chemical studies on synthetic dyes and its application " Faculty of Science , Al – Azhar University, (2007) .
9. F., Hassan M.Sc .Thesis " Preparation of some safety Dyes and Natural Identical dyes " Faculty of Science , Al-Azhar University (2007) .
10. A.P., Towns, *Dyes and Pigments*, 42, 3, (1999).